

PERFORMANCE OF CERAMIC MEMBRANE COATED WITH GRAPHENE OXIDE AS ALTERNATIVE FOR OILY WASTEWATER TREATMENT

(Prestasi Selaput Seramik Grafin Oksida Sebagai Pilihan Untuk Rawatan Air Sisa Berminyak)

Nurdiyana Nabilah Kasim¹, Sharifah Abdullah¹, Nur Asmaliza Mohd Noor^{2*}

¹Faculty of Civil Engineering,

Universiti Teknologi MARA, 40450 Shah Alam, Selangor, Malaysia

²Faculty of Civil Engineering,

Universiti Teknologi MARA Pahang, Lintasan Semarak 26400 Jengka, Pahang, Malaysia

*Corresponding author: nurasmaliza@uitm.edu.my

Received: 20 November 2019; Accepted: 5 April 2020; Published: 9 June 2020

Abstract

The high demand for liquefied natural gas (LNG) contributes to the increasing production of LNG thus leading to the increment of oily wastewater. The membrane technology shows a very promising alternative to replace the conventional method to treat oily wastewater. The objectives of this study are to synthesize graphene oxide (GO) as a modifier to graphitic carbon nitride ($g-C_3N_4$) for alumina ceramic membrane, to characterize the structure of nanosheet and bulk of graphitic carbon nitride, graphene oxide and $g-C_3N_4/GO$ composite which leads to the study of the performance of $g-C_3N_4/GO$ coated alumina ceramic photocatalytic membrane to degrade oil in oily wastewater. The methodology started with the material preparation, photocatalyse membrane preparation and the characterization of material using X-ray diffraction (XRD), Fourier Transformation Infrared (FTIR) analysis, Brunauer Emmet Teller (BET) surface area analyses and UV-Vis-NIR spectrophotometer analysis. The last method is the degradation of methylene blue (MB) dye and photocatalytic study degradation of oil in wastewater using synthesis oily wastewater. The results indicated the $g-C_3N_4/GO$ reduced 73.79% of the MB dye compared to 38.85% and 62.71% for bulk $g-C_3N_4$ and $g-C_3N_4$ nanosheet respectively. The $g-C_3N_4/GO$ composite photocatalyst showed remarkable photocatalytic efficiency rather than bulk $g-C_3N_4$ and $g-C_3N_4$ nanosheet. Thus, the introduction of GO into $g-C_3N_4$ has improved the charge separation efficiency of $g-C_3N_4$ and improving the organic degradation potential of $g-C_3N_4$.

Keywords: alumina, $g-C_3N_4$, graphene oxide, photocatalytic membrane, oily wastewater

Abstrak

Permintaan yang tinggi terhadap gas asli cecair (LNG) menyumbang kepada peningkatan pengeluaran LNG sehingga mengakibatkan pertambahan terhadap air sisa berminyak. Teknologi selaput menjadi pilihan yang menggantikan kaedah konvensional dalam merawat air sisa berminyak. Objektif kajian ini adalah untuk melakukan sintesis grafin oksida (GO) sebagai pengubahsuai karbon nitrida grafit ($g-C_3N_4$), untuk memperincikan struktur lapisan nano, karbon nitrida grafit, grafin oksida dan $g-C_3N_4/GO$ komposit yang membawa kepada kajian prestasi selaput fotomangkin seramik alumina bersalut $g-C_3N_4/GO$ untuk degradasi minyak dalam air sisa berminyak. Kaedah kajian bermula dengan penyediaan bahan, penyediaan selaput fotomangkin dan pencirian bahan menggunakan pembelauan sinar-X (XRD), analisis inframerah transformasi Fourier (FTIR), analisis kawasan permukaan Brunauer Emmet Teller (BET) dan analisis spektrofotometer UV-Vis-NIR. Kaedah terakhir adalah degradasi pewarna metilena biru (MB) dan kaedah fotomangkin dalam degradasi minyak dalam air sisa menggunakan jenis

tiruan. Keputusan kajian ini telah menunjukkan bahawa g-C₃N₄/GO berkurang kepada 73.79% daripada pewarna MB berbanding 38.85% untuk g-C₃N₄ dan 62.71% untuk g-C₃N₄ lapisan nano. Manakala kaedah fotomangkin bagi komposit g-C₃N₄/GO menunjukkan kecekapan fotomangkin yang luar biasa berbanding g-C₃N₄ dan g-C₃N₄ lapisan nano. Oleh itu, pengenalan GO ke dalam g-C₃N₄ telah meningkatkan kecekapan g-C₃N₄ sebagai agen pemisahan sekali gus meningkatkan potensi g-C₃N₄ sebagai degradasi organik.

Kata kunci: alumina, g-C₃N₄, grafin oksida, fotokatalik, selaput, air sisa berminyak

Introduction

Numerous processes and activities in various industries that have led to the production of wastewater are food processing, textile and oil and gas. In Malaysia, oil and gas industries are the major contribution in economy and thus a lot of activities related to these industries and causing major contribution to the production of wastewater. There are a few activities in oil and gas that produces wastewater such as raw natural gas that is fed into gas treating facilities such as acid gas removal unit (AGRU), mercury removal unit, and dehydration unit and then passed into the liquefaction unit to convert it into LNG. These units' associated facility leads to the generation of wastewater which can be divided into the conventional and non-conventional pollutants. The types of conventional pollutants which are also known as oily wastewater are oil and grease and suspended solids while the non-conventional pollutants which are known as chemically contaminated wastewater are phenolic compounds, sulphide and ammonia [1]. In this study, oily wastewater is emphasized due to the increase of its group therefore the proper and better oily wastewater treatment technology or strategies are needed to tackle these issues. It is necessary to purify the wastewater in order to meet the environment's discharge standards by the Department of Environment (DOE) Malaysia because oily wastewater can cause adverse effects to the environment especially marine life as shown in Table 1 [2].

New technology has been introduced to treat oily wastewater using the membrane [3] where it has a function to act as a selective barrier to separate the pollutants from water. Previously, most of the studies have been conducted to improve the efficiency of alumina ceramic membrane to separate and treat wastewater. However recently, the addition of the degradation capability to facilitate the membrane separation process using photocatalyst such as carbon nitride, g-C₃N₄ on the surface of the ceramic membrane as quite a promising method has been introduced. Despite the fact that the membrane presents great potential to be applied in the separating process, yet it has fouling problems [4]. The fouling is hard to be removed and it could weaken the permeation rate through the membrane and affect the quality of treated wastewater [3]. Thus, the introduction of photocatalyst on the surface of the membrane could contribute antifouling functions under light irradiation, sustain the clean membrane surface and improve the quality of treated wastewater. Therefore, the objectives of this study are to synthesize graphene oxide (GO) as a modifier to graphitic carbon nitride (g-C₃N₄) for alumina ceramic membrane, to characterize the structure of nanosheet and the bulk of graphitic carbon nitride, graphene oxide and g-C₃N₄ /GO composite and to study the performance of g-C₃N₄/GO coated alumina ceramic photocatalytic membrane to degrade oil in oily wastewater.

Table 1. Discharge of industrial effluent or mixed effluent of standard A and B [2]

Parameter	Unit	Standard A	Standard B
Temperature	⁰ C	40	40
pH Value	-	6.0-9.0	5.5-9.0
BOD ₅ at 20 ⁰ C	mg/L	20	50
Suspended Solid	mg/L	50	100
Mercury	mg/L	0.005	0.05
Cadmium	mg/L	0.01	0.02
Chromium Hexavalent	mg/L	0.05	0.05
Chromium Trivalent	mg/L	0.20	1.0
Arsenic	mg/L	0.05	0.10
Cyanide	mg/L	0.05	0.10
Lead	mg/L	0.10	0.50
Copper	mg/l	0.20	1.00
Manganese	mg/L	0.20	1.00
Nickel	mg/L	0.20	1.00
Tin	mg/L	0.20	1.00
Zinc	mg/L	2.00	2.00
Boron	mg/L	1.00	4.00
Iron (Fe)	mg/L	1.00	5.00
Silver	mg/L	0.10	1.00
Aluminum	mg/L	10	15.0
Selenium	mg/L	0.02	0.50
Barium	mg/L	1.0	2.00
Fluoride	mg/L	2.0	5.00
Formaldehyde	mg/L	1.0	2.00
Phenol	mg/L	0.001	1.00
Free Chlorine	mg/L	1.0	2.00
Sulphide	mg/L	0.05	0.05
Oil and Grease	mg/L	1.0	10
Ammoniacal Nitrogen	mg/L	10	20
Color	ADMI	100	200

Materials and Methods

To achieve the objectives of this study, the methodology can be divided into 4 Parts. Part 1 covers the material preparation, that is, synthesis of bulk graphitic carbon nitride synthesis of bulk graphitic carbon nitride ($g\text{-C}_3\text{N}_4$) nanosheet and synthesis of GO. Part 2 involves the photocatalyst membrane preparation, that is, synthesis alumina ceramic, disc membrane, preparation of ceramic dope solution, fabrication of alumina ceramic disc membrane and synthesis of $g\text{-C}_3\text{N}_4/\text{GO}$ alumina ceramic membrane. The work on material characterization of materials is done in Part 3 utilizing analyzes *via* XRD, FTIR, BET and UV-Vis-NIR. The last part which is Part 4 involves related pre photocatalysis studies such as degradation measurement of methylene blue (MB) dye and photocatalytic studies on the degradation of oil in wastewater using synthetic oily wastewater. Details of each above-mentioned methodology parts are discussed as follows:

Material preparation

The facile temperature free method was used for preparation of $g\text{-C}_3\text{N}_4$ by using urea powder (HmbG Chemical Germany) and isopropanol alcohol (IPA, 99.7%, $M = 60.10$ g/mol) bought from Hypercube IT Solution as dispersion medium to exfoliate the bulk $g\text{-C}_3\text{N}_4$ into $g\text{-C}_3\text{N}_4$ nanosheet. GO was prepared by Hummers' method by using graphite powder (Comak) and sodium nitrate (System, NaNO_3 , ChemAR). Sonochemical method was used to prepare $g\text{-C}_3\text{N}_4/\text{GO}$ composite.

Synthesis of bulk graphitic carbon nitride

The synthesis of bulk graphitic carbon nitride is achieved using the urea powder by applying facile template-free method [6]. An amount 20 g of urea powder purchased from HmbG Chemical was settled in a lidded alumina crucible and heated for 550°C in a carbolite furnace for 4 hours using the heating rate of $15^\circ\text{C}/\text{min}$.

Synthesis of bulk $g\text{-C}_3\text{N}_4$ nanosheet

Nanosheet form of $g\text{-C}_3\text{N}_4$ was synthesized using the liquid exfoliation method of $g\text{-C}_3\text{N}_4$ [7] in order to

have improved photocatalytic effect. This method used organic solvent isopropanol alcohol (IPA, 99.7%, $M = 60.10$ g/mol) brought from Hypercube IT Solution as a dispersion medium where 0.3 g of bulk graphitic carbon nitride was dispersed into 100 mL of isopropanol alcohol. The dispersion was sonicated in room temperature for 8 hours to exfoliate the bulk $g\text{-CN}$ then centrifuged at 3000 rpm for 30 minutes in order to give the homogenous dispersion of exfoliated $g\text{-C}_3\text{N}_4$ nanosheet. After that, the dispersion was dried at 50°C for 6 hours in order to form and collect the final product which was a light-yellow powder of $g\text{-C}_3\text{N}_4$ nanosheet.

Synthesis of GO

GO was synthesized using the Hummers' method [8] where 5 g of graphite powder and 2.5 g of sodium nitrate was put in 1000 mL of concentrated sulphuric acid (H_2SO_4). Subsequently, the mixture was stirred for 1 hour and kept under low temperature by placing it in ice. After that, the 30 g of KMnO_4 was gradually added for 2 hours and continuously stirred for another 2 hours in room temperature and then heated with a temperature of 70°C . Next, the 100 mL of water was gradually added to the mixture and stirred for another 1 hour. The 30 mL of H_2O_2 was added into the mixture to stop the reaction and the color of the suspension turned to bright yellow. In order to purify the suspension, 0.2M of HCl was added once and the 200 mL of distilled water, 3 times until pH 7 (neutral). Then the sample was dried in the furnace with a temperature of 80°C for a day in order to form GO.

Synthesis of $g\text{-C}_3\text{N}_4/\text{GO}$ composite photocatalyst

The synthesis followed the sonochemical method ([9]) where 0.2 g of GO of previous synthesis was added into 200 mL of high purity water, 0.2g of $g\text{-C}_3\text{N}_4$ nanosheet was added into the mixture, sonicated for 12 hours, furnace dried in a temperature of 80°C for a day.

Photocatalyst membrane preparation

This part started with the synthesis of alumina ceramic disc membrane as it was used as the base membrane in

this study. The other steps for preparation for photocatalyst membrane are as follows:

Preparation of ceramic dope solution

The ceramic dope solution was prepared first for the process fabrication of the ceramic membrane. It consisted of the composition of ceramic particle, a polymeric binder, solvent, additive that acts as the dispersant [10]. The ceramic particle was used as Al_2O_3 , alpha; 99.9% metal basis, surface area $6\text{--}8\text{ m}^2/\text{g}$, $<1.0\text{-micron}$ APS powder, Alfa Aesar for this research. Meanwhile dimethyl sulfoxide (HPLC grade, VWR), and polymeric binder polyethersulfone (PESf, Ameco Performance, USA) were used. Arlacel P135 (polyethylene glycol 30-dipolyhydroxystearate, Uniqema) was used as the additive. The process of preparation started with 55 wt.% of aluminum oxide powder, 0.38 wt.% of Arlacel weighed and added into 39.12 wt.% of the solvent, DMSO. Additionally, the mixture was rolled/milled with grinding balls for 48 hours. The ceramic dope solution was ready to be used to fabricate the ceramic disc membrane after adding 5.5 wt.% of PESf into the mixture and rolled for another 48 hours.

Fabrication of alumina ceramic disc membrane

The ceramic dope solution went through the inversion method where it needs to be poured into a stainless-steel mold with a diameter of 3 cm and placed in a water bath for 30 minutes and after it hardens, the precursor ceramic disk was removed. The next process was sintering the precursor ceramic disc calcite by using furnace CARBOLITE to obtain the final ceramic disc membrane. The temperature of the furnace was set at $600\text{ }^\circ\text{C}$ at a rate of $2\text{ }^\circ\text{C}/\text{minute}$ with a dwell time of 2 hours and has been increased to the targeted temperature of $1400\text{ }^\circ\text{C}$ at a rate of $5\text{ }^\circ\text{C}/\text{minute}$ with a dwell time of 4 hours. Then, the temperature was reduced to room temperature at a rate of $5\text{ }^\circ\text{C}/\text{minute}$ and the alumina ceramic membrane was ready to be coated with the composite photocatalyst.

Synthesis of $\text{g-C}_3\text{N}_4/\text{GO}$ alumina ceramic membrane

The 0.3 g of $\text{g-C}_3\text{N}_4/\text{GO}$ composite was dissolved in 50 mL of distilled water and sonicated for 1 hour. Then, $\text{g-C}_3\text{N}_4/\text{GO}$ solution was coated with alumina ceramic membrane by pouring the solution on the ceramic membrane surface and dried in the furnace at $50\text{ }^\circ\text{C}$ for a day.

$\text{C}_3\text{N}_4/\text{GO}$ solution was coated with alumina ceramic membrane by pouring the solution on the ceramic membrane surface and dried in the furnace at $50\text{ }^\circ\text{C}$ for a day.

Characterization of material

Characterization of material for synthesized GO, bulk and nanosheet $\text{g-C}_3\text{N}_4$ and $\text{g-C}_3\text{N}_4/\text{GO}$ composites used the XRD method which operated with 40 kV and 40 mA and the scanning rate was $2\text{ }^\circ/\text{minute}$. Besides, the FTIR was also used to characterize the material with the operation of wavelength around $800\text{--}3800\text{ cm}^{-1}$. Other methods that used to characterize material was BET Surface Area Analysis where the specific surface area and pore size distribution of synthesized materials in powder was determined by the adsorption of nitrogen gas on the surface of the solid powder by calculating the amount of adsorbate gas on the layer of surface. It was done by using 3-Flex Micromeritics system. As for determination of degradation rate of MB dye and oily wastewater, the UV-Vis-NIR spectrophotometer (Perkin Elmer, LAMBDA 750) was used to obtain spectra.

Photocatalytic study: Degradation of MB dye

The preliminary photodegradation study was conducted on MB dye by using bulk $\text{g-C}_3\text{N}_4$, $\text{g-C}_3\text{N}_4$ nanosheet, and $\text{g-C}_3\text{N}_4/\text{GO}$ composite powder under sunlight. An amount 0.1 g of each material added into a beaker that contained 50 mL of 25 mg/L MB dye. Then the solution was placed under sunlight for 2 hours and for every 30 minutes, 3 mL of solutions was extracted using a syringe and this was used to analyze and determine the degradation efficiency by using the UV-Vis-NIR Spectrophotometer at $\lambda > 400\text{ nm}$.

Photocatalytic study: Degradation of oil in wastewater

Photodegradation study on synthetic oily wastewater was conducted by using $\text{g-C}_3\text{N}_4/\text{GO}$ composite powder. The synthetic oily wastewater was prepared by mixing 1 L of distilled water and of 1 mL West Lutong light crude oil (SG 0.84, API 37.7) in room temperature but under sunlight. Then, an amount 0.1g of $\text{g-C}_3\text{N}_4/\text{GO}$ composite was added into a beaker which contained 50 mL oily wastewater. The solutions were needed to be

placed under sunlight for 2 hours, 3 mL of solution was extracted using a syringe for every 30 minutes to determine the degradation efficiency using UV-Vis-NIR spectrophotometer.

Results and Discussion

Characterization of material: XRD analysis

Figure 1 shows the XRD pattern of fabricated bulk $g\text{-C}_3\text{N}_4$ and $g\text{-C}_3\text{N}_4$ nanosheet. Two peaks were identified for both $g\text{-C}_3\text{N}_4$ where for bulk $g\text{-C}_3\text{N}_4$, dominant (002) diffraction peak was identified at $2\theta = 27.2^\circ$. It was indicated in the interlayer stacking of conjugated aromatic CN unit with $d = 3.27 \mu\text{m}$. The improvement of (002) peak's intensity was found in $g\text{-C}_3\text{N}_4$ nanosheet due to the enhancement in crystallinity of $g\text{-C}_3\text{N}_4$ after liquid exfoliation [11]. The small degree of shifting in (002) diffraction peak's point was identified from 27.2° in bulk $g\text{-C}_3\text{N}_4$ to 27.4° in $g\text{-C}_3\text{N}_4$ nanosheet. The same goes to the stacking distance from $d = 3.27 \mu\text{m}$ in bulk $g\text{-C}_3\text{N}_4$ to $d = 3.25 \mu\text{m}$. Both bulk $g\text{-C}_3\text{N}_4$ and $g\text{-C}_3\text{N}_4$ nanosheet indicated minor (100) diffraction peak around 13.0° which corresponds to the in-plane structural packing of triazine units while the distance between pores of nitride in $g\text{-C}_3\text{N}_4$ are specified with planar distance of $d = 6.79 \mu\text{m}$ for (100) diffraction peak. The diffraction peak at a lower angle of about 11.4° GO implies the introduction of oxygen containing functional group of GO [12,13].

The XRD patterns of fabricated $g\text{-C}_3\text{N}_4$ nanosheet, GO and $g\text{-C}_3\text{N}_4/\text{GO}$ composite are shown in Figure 2. GO shows intense (001) diffraction peak at $2\theta = 9.8^\circ$ which is typical for GO and the same pattern has been reported by Dutrow and Clark [11]. The factors that contributed to that pattern were the existence of oxygenated functional group and introduction of H_2O molecule. A study conducted by Olumurewa et al. [14] indicated that the introduction of diffraction peak at low angle furnace that the graphite was successfully oxidized to the GO. The XRD pattern for $g\text{-C}_3\text{N}_4/\text{GO}$ composite showed the two diffraction peaks which was around 27.3° and this was quite similar with the XRD pattern of $g\text{-C}_3\text{N}_4$ (002) peak thus indicating that the composite contains $g\text{-C}_3\text{N}_4$. This was consistent with the findings by Alam et al. [15] that introduction of GO into the $g\text{-C}_3\text{N}_4$ did not affect the structure of $g\text{-C}_3\text{N}_4$. The introduction of GO has caused the intensity of (002) diffraction peak of $g\text{-C}_3\text{N}_4/\text{GO}$ to decrease and this proved that $g\text{-C}_3\text{N}_4/\text{GO}$ has less layers than $g\text{-C}_3\text{N}_4$ and this is parallel with the report by Dutrow and Clark [11]. Besides that, the modification of GO into $g\text{-C}_3\text{N}_4$ also caused the widening of (002) diffraction peak and this condition was explained by authors, where it is caused by the wavelike motion of the layer of $g\text{-C}_3\text{N}_4/\text{GO}$ composite.

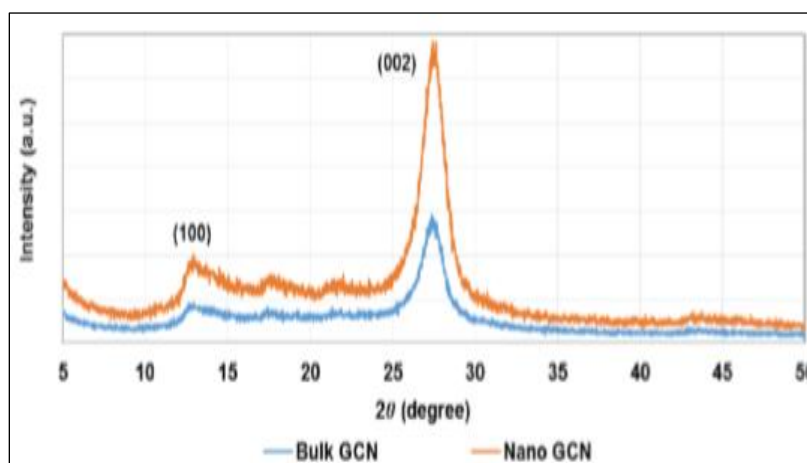


Figure 1. XRD pattern for bulk $g\text{-C}_3\text{N}_4$ and $g\text{-C}_3\text{N}_4$ nanosheet

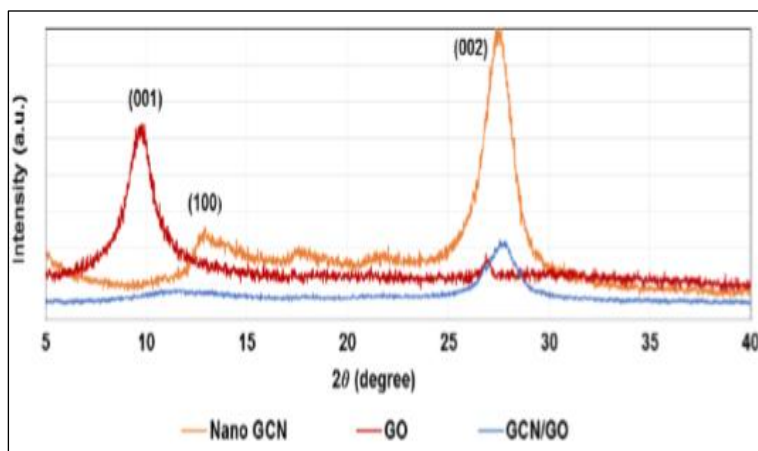


Figure 2. XRD patterns of g-C₃N₄ nanosheet, GO and g-C₃N₄/GO composite

FTIR analysis

Figure 3 shows FTIR spectrum of fabricated bulk g-C₃N₄ and g-C₃N₄ nanosheet with the wide absorption band at 3000 - 3400 cm⁻¹. According to Sheha [16], this is caused by the hydroxyl group due to the adsorption of H₂O molecule and uncondensed amine (-NH₂) or amine (-CH=NH). FTIR spectra of bulk g-C₃N₄ and g-C₃N₄ showed that at 1200 and 1220 cm⁻¹ respectively due to the characteristics of the breathing mode of heptazine ring system [17]. FTIR spectrum of bulk g-C₃N₄ and g-C₃N₄ nanosheet in Figure 3 are clearly identified and can be concluded that the exfoliation of g-C₃N₄ still retain their chemical structure as bulk g-C₃N₄ and this is aligned with the study conducted by Raphael [18].

The FTIR spectrum of g-C₃N₄/GO composite shows the resemblance pattern to the FTIR spectrum of g-C₃N₄ but with a slight difference to the GO as shown in Figure 4. The spectrum of GO shows the wider absorption band at a range of 3000-3500 cm⁻¹ attributed by the stretching of OH group of water molecules. Meanwhile, the g-C₃N₄/GO composite shows the same pattern of absorption band as GO and this is contributed by the stretching of N-H group. The g-C₃N₄/GO composite exhibited the sharp peak at 804.19 cm⁻¹ and the g-C₃N₄ nanosheet depicted the sharp peak at 1220 cm⁻¹. [19] conducted a study and found that the peak at 1039.31 cm⁻¹ caused by the presence of the

C-O functional group. Literature study [20] described that the peak at 1618.65 cm⁻¹ was contributed by C=O stretching when at this stage the C=C bonds are still intact even after the oxidation process. Thus, this finding supports the justification for XRD analysis by introducing the GO into g-C₃N₄ and not altering the chemical structure of g-C₃N₄.

BET analysis

Table 1 shows the value of surface area and pore volume of bulk g-C₃N₄, g-C₃N₄ nanosheet, g-C₃N₄/GO composite and GO that was identified through the BET analysis.

The g-C₃N₄ nanosheet indicated the greater surface area and large pore volume compared to the other materials. The liquid exfoliation of bulk g-C₃N₄ has been minimized to the size of the nanometer thus the increase of specific areas for g-C₃N₄ was due to the bond cleavage of g-C₃N₄. BET surface area of g-C₃N₄ nanosheet was 94.08 m²/g greater than bulk g-C₃N₄ that was 79.84 m²/g as shown in Table 1. According to [21] the high surface area of g-C₃N₄ nanosheet would have the significant presence of active sites with nitrogen atom where it is very suitable to be used as a photocatalyst. Meanwhile, the BET surface area of GO and g-C₃N₄/GO composite were 2.01 m²/g and 45.57 m²/g respectively. These results have been agreed with the results produced by Vlachos et al. [22].

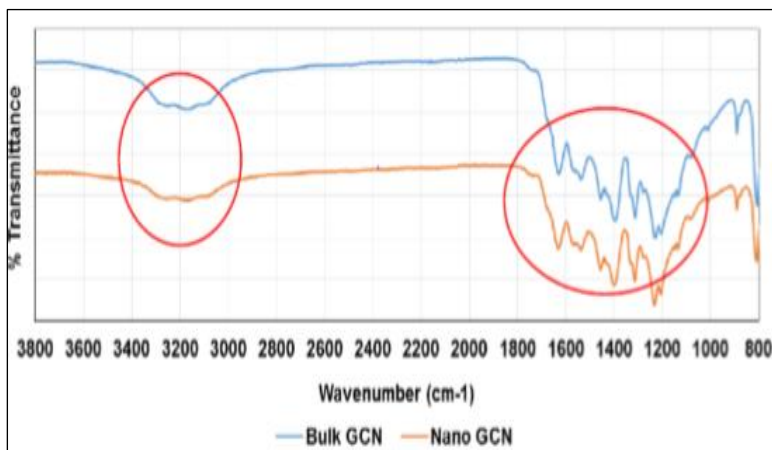


Figure 3. FTIR spectrum of bulk $g\text{-C}_3\text{N}_4$ and $g\text{-C}_3\text{N}_4$ nanosheet

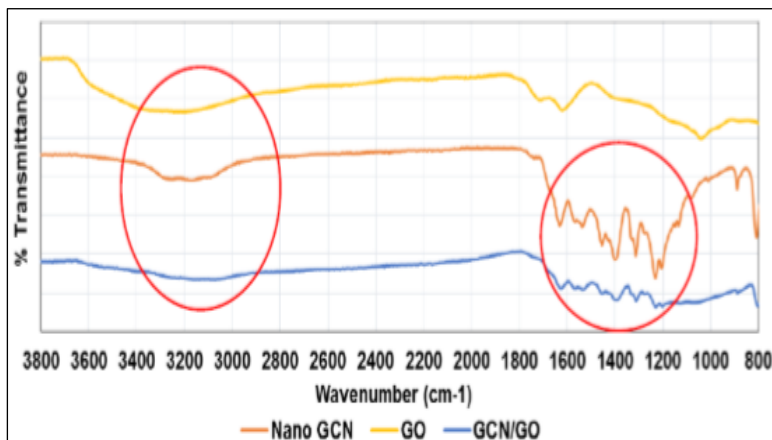


Figure 4. FTIR spectrum of $g\text{-C}_3\text{N}_4$ nanosheet, GO and $g\text{-C}_3\text{N}_4/\text{GO}$ composite

Table 1. BET surface area and pore volume of material

Sample Name	Sample Mass (g)	SBET (m^2/g)	Pore Volume (cm^3/g)
Bulk $g\text{-C}_3\text{N}_4$	0.086	79.840	0.465
$g\text{-C}_3\text{N}_4$ nanosheet	0.048	94.079	0.639
$g\text{-C}_3\text{N}_4/\text{GO}$	0.224	45.572	0.057
GO	0.188	2.010	0.003

Photocatalytic study

Degradation of MB dye

Photocatalysis is the method to measure the acceleration of chemical conversion through the activation of a catalyst. The preliminary photo-degradation study under sunlight study was conducted on MB dye by using bulk $g\text{-C}_3\text{N}_4$, $g\text{-C}_3\text{N}_4$ nanosheet and $g\text{-C}_3\text{N}_4/\text{GO}$ composite powder. Figure 5 shows the process of photocatalytic degradation of MB dye under sunlight for bulk $g\text{-C}_3\text{N}_4$, $g\text{-C}_3\text{N}_4$ nanosheet and $g\text{-C}_3\text{N}_4/\text{GO}$ composite powder. The photocatalytic potential for different photocatalysts was evaluated by comparing the degradation efficiency for MB dye. The amount of MB dye degradation is 42.75% for $g\text{-C}_3\text{N}_4/\text{GO}$ composite, 50.77% for $g\text{-C}_3\text{N}_4$ nanosheet and 31.29% for bulk $g\text{-C}_3\text{N}_4$ after 1 hour of exposure to sunlight can be seen through Figure 5. However, after 2 hours of exposure to sunlight, the amount of MB dye degradation has increased to 73.79% for $g\text{-C}_3\text{N}_4/\text{GO}$ composite, 62.71% for $g\text{-C}_3\text{N}_4$ nanosheet and 38.85% for bulk $g\text{-C}_3\text{N}_4$. According to the findings, the bulk $g\text{-C}_3\text{N}_4$ and $g\text{-C}_3\text{N}_4$ nanosheet depicted the reduction of degradation efficiency after 30 minutes and 90 minutes of exposure to sunlight. However, the $g\text{-C}_3\text{N}_4/\text{GO}$ composite indicated the consistency of the degradation efficiency throughout 2 hours of exposure. The $g\text{-C}_3\text{N}_4$ is to be the potential photocatalysts for the degradation of numerous pollutants with photophysical potential of the parent nitride altered through doping with heteroatoms, heterojunction formation with other materials and textural enhancements to expand the surface area and porosity [23].

Thus, the finding showed that the $g\text{-C}_3\text{N}_4/\text{GO}$ composite has a good degradation capability followed by $g\text{-C}_3\text{N}_4$ nanosheet and bulk $g\text{-C}_3\text{N}_4$. The photocatalyst potential of $g\text{-C}_3\text{N}_4/\text{GO}$ composite was contributed by its characterization of chemical structure and properties. The introduction of GO has improved the charge of separation efficiency because when the visible light absorption capability $g\text{-C}_3\text{N}_4$ is combined with GO they act as electron sink [22] in helping the separation and storage to improve the photocatalytic capability of the composite. When $g\text{-C}_3\text{N}_4$ absorbed visible light, the electron is transferred to the GO layer where it reduces the chances of

electron-hole recombination thus improving the separation efficiency. However, the left holes on the valence band of $g\text{-C}_3\text{N}_4$ contributed to the consistent degradation efficiency of $g\text{-C}_3\text{N}_4/\text{GO}$ composite. The factor that bulk $g\text{-C}_3\text{N}_4$ is having the lowest degradation efficiency compared to $g\text{-C}_3\text{N}_4$ nanosheet due to the low surface area where active site is less thus a low number of MB dye molecule is interacted with the photoexcited carrier [24]. As for $g\text{-C}_3\text{N}_4$ nanosheet, it slightly contradicts where it had a greater surface area thus greater availability of active sites to react with MB dye molecule.

Degradation of oil in wastewater

The potential of bulk $g\text{-C}_3\text{N}_4$, $g\text{-C}_3\text{N}_4$ nanosheet and $g\text{-C}_3\text{N}_4/\text{GO}$ composite to degrade organic pollutants were tested with the evaluation of the efficiency of photocatalyst to degrade oil in synthetic oily wastewater under sunlight. Figure 6 shows the photocatalytic degradation of oil in synthetic oily wastewater under sunlight with bulk $g\text{-C}_3\text{N}_4$, $g\text{-C}_3\text{N}_4$ nanosheet and $g\text{-C}_3\text{N}_4/\text{GO}$ composite powder. The $g\text{-C}_3\text{N}_4/\text{GO}$ composite shows the consistent degradation efficiency after 1 hour with 49.65% of oil degraded while the bulk $g\text{-C}_3\text{N}_4$ only degraded to 35.24% of oil. After 2 hours, the results indicated that the amount of oil degraded was 75.54%, 55.89% and 44.57% for $g\text{-C}_3\text{N}_4/\text{GO}$ composite, $g\text{-C}_3\text{N}_4$ nanosheet and bulk $g\text{-C}_3\text{N}_4$ respectively. The samples also produced initially, strong aromatic smells however, after 2 hours, the $g\text{-C}_3\text{N}_4/\text{GO}$ composite produced a less aromatic smell. [25,26] also conducted a study using low cost ceramic membrane to treat synthetic oily wastewater and it showed a capability to treat oily wastewater.

Performance of $G\text{-C}_3\text{N}_4/\text{GO}$ alumina ceramic membrane

Figure 7 shows the process of separation and photocatalytic degradation of oil in synthetic oily wastewater in bare alumina ceramic membrane and $g\text{-C}_3\text{N}_4/\text{GO}$ alumina ceramic membrane. From the results obtained, the $g\text{-C}_3\text{N}_4/\text{GO}$ alumina ceramic membrane showed a greater percentage of oil adsorption compared to the bare alumina ceramic membrane with 47.65% and 27.66% respectively after 2 hours. After the degradation and separation process, permeate water of $g\text{-C}_3\text{N}_4/\text{GO}$ alumina ceramic membrane looked

clearer compared to the permeated water of bare alumina ceramic membrane according to the clarity of red scale. Moreover, there was no change in the intensity of aromatic smell of wastewater for both samples thus indicating that the aromatic compound is mostly not degraded. The coating of g-C₃N₄/GO on alumina ceramic membrane also had a greater removal efficiency of oil in oily wastewater rather than the bare

alumina ceramic membrane. This is due to the separation process of alumina ceramic membrane coupled with the degradation process of oil in the wastewater by gC₃N₄/GO [27]. In conclusion, g-C₃N₄/GO alumina ceramic membrane can be a potential candidate to treat the industrial oily wastewater.

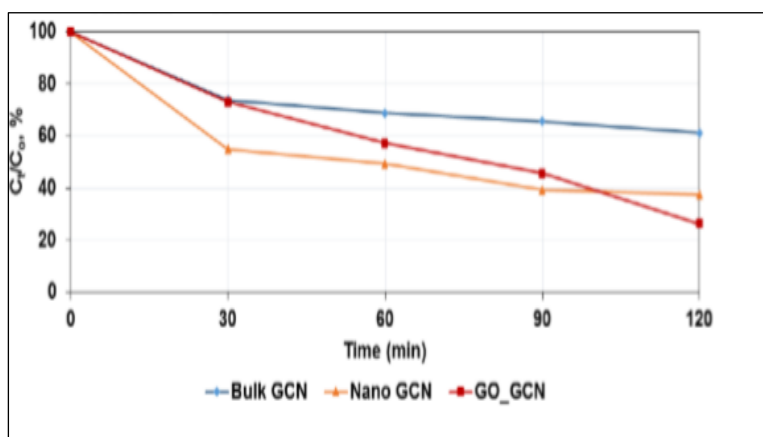


Figure 5. Photocatalytic degradation of MB dye under sunlight with bulk g-C₃N₄, g-C₃N₄ nanosheet, and g-C₃N₄/GO composite

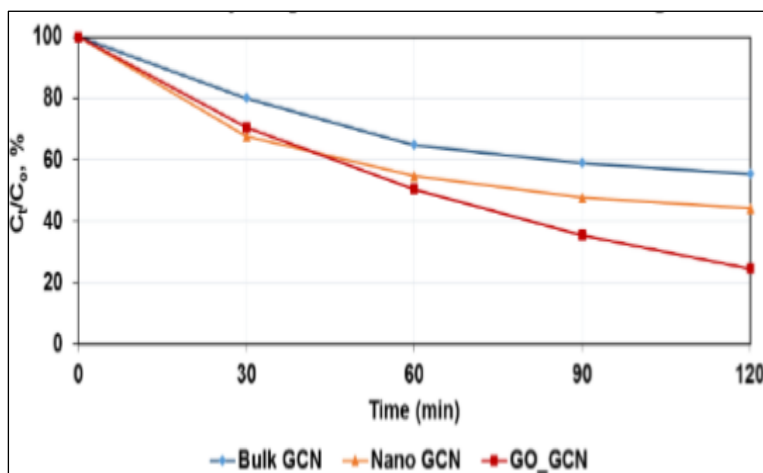


Figure 6. Photocatalytic degradation of oil in wastewater under sunlight with bulk g-C₃N₄, g-C₃N₄ nanosheet and g-C₃N₄/GO composite

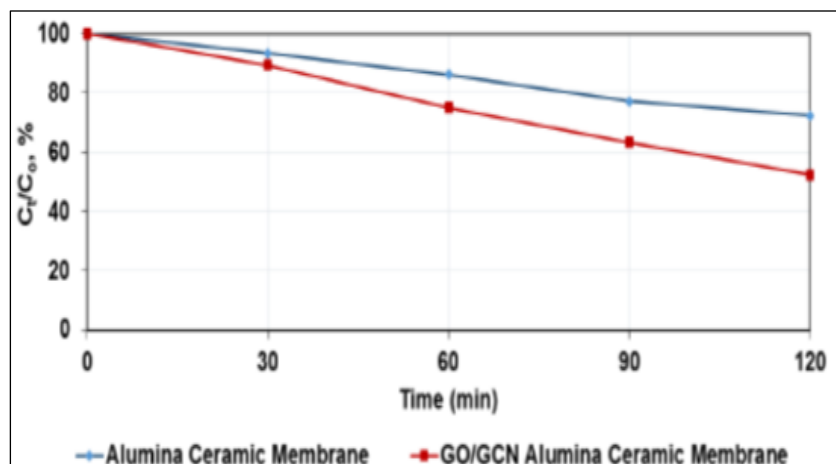


Figure 7. Separation and degradation of oil in synthetic oily wastewater with g-C₃N₄/GO alumina membrane and bare alumina membrane

Thus g-C₃N₄/GO alumina ceramic membrane shows good removal capability of oil in oily wastewater when compared to bare alumina ceramic membrane. The improvement of the performance of alumina ceramic membrane to remove oil in the wastewater was contributed by the introduction of photocatalyst g-C₃N₄/GO on the membrane surface. The additional g-C₃N₄/GO photocatalyst opened up a new process that the degradation facilitates the removal of the organic compound of oil hence improving the quality of the permeated water

Conclusion

GO, photocatalyst bulk g-C₃N₄, g-C₃N₄ nanosheet and g-C₃N₄/GO composites were successfully synthesized and a major enhancement of photocatalytic potential under sunlight was achieved through the g-C₃N₄/GO composite. According to the results of XRD analysis, bulk g-C₃N₄ and g-C₃N₄ nanosheet shows the dominant (002) diffraction peaks at $2\theta = 27.2^\circ$ and $2\theta = 27.4^\circ$ which validated that the materials prepared were correct. Besides, g-C₃N₄ shows improvement of (002) peak's intensity rather than bulk g-C₃N₄ due to the enhancement in crystallinity of g-C₃N₄ after liquid exfoliation. GO also successfully prepared and proved by results of XRD analysis where major (001) diffraction peak at $2\theta = 9.8^\circ$. For FTIR analysis, a wide absorption band at 3000 – 4000 cm⁻¹ was

identified for both bulk g-C₃N₄ and g-C₃N₄ nanosheet where it was indicated that both had hydroxyl groups in the structure. Both photocatalysts also indicated an absorption band at 1203 – 1628 cm⁻¹ due to stretching of CN units in aromatic ring (RSC). FTIR spectrum of g-C₃N₄/GO showed the wide absorption band at 3000 – 3400 m⁻¹ of FTIR spectrum which was close to the g-C₃N₄ which was attributed by stretching of the N-H group. This further strengthened the conclusion that introduction of GO into g-C₃N₄ did not alter the chemical structure of g-C₃N₄.

The BET analysis showed that g-C₃N₄ nanosheet has a greater surface area than bulk g-C₃N₄ and g-C₃N₄/GO where the results are 94.08 m²/g, 79.84 m²/g and 2.01 m²/g respectively. The exfoliation of bulk g-C₃N₄ has minimized the size of the particle and improved the specific area of g-C₃N₄. This indicated that the exfoliation process was successful and the g-C₃N₄ bond was cleaved. The surface area of g-C₃N₄/GO was lower due to the stacking of layers on the structure of materials. The major enhancement of photocatalytic potential under sunlight was achieved by using g-C₃N₄/GO composite. The introduction of GO into g-C₃N₄ had improved the charge separation efficiency of g-C₃N₄ which enhanced the capability of g-C₃N₄ to MB and oil in oily wastewater. A g-C₃N₄/GO degraded 73.79% of MB dye rather than 38.85% and 62.71% for

bulk g-C₃N₄ and g-C₃N₄ nanosheet. g-C₃N₄/GO also degraded 75.54% of oil greater than bulk g-C₃N₄ and g-C₃N₄ nanosheet was 44.57% and 55.89% respectively. The exfoliation of g-C₃N₄ also showed a significant improvement in degradation capability of the g-C₃N₄ where, g-C₃N₄ nanosheet has a larger surface area with abundant active sites to react with photoexcited carriers compared to the bulk g-C₃N₄.

References

- Jacobs, D. (2011). The global market for liquefied natural gas. *Reserve Bank Australian Bulletin*, 9: 17-28.
- Department of Environment (2009). Discharge of industrial effluent or mixed effluent of standard A and B. Access from <http://www.doe.gov.my/eia/wp-content/uploads/2012/03/A-Guide-For-Investors1.pdf>. [Access online 20 March 2020].
- Coca, J., Gutiérrez, G. and Benito, J. M. (2011). Treatment of oily wastewater. *NATO Science Peace and Security. Series C Environment Security*, 101: 1-55.
- Won, W., Lee, S. K., Choi, K. and Kwon, Y. (2014). Current trends for the floating liquefied natural gas (FLNG) technologies. *Korean Journal of Chemical Engineering*, 31: 732-743.
- De Angelis, L. and De Cortalezzi, M. M. F. (2013). Ceramic membrane filtration of organic compounds: Effect of concentration, pH, and mixtures interactions on fouling. *Separation and Purification Technology*, 118: 762-775.
- Goettmann, F., Thomas, A. and Antonietti, M. (2007). Metal-free activation of CO₂ by mesoporous graphitic carbon nitride. *Angewandte Chemie - International Edition*, 46(15): 2717-2720.
- Liu, J., Zhang, T., Wang, Z., Dawson, G. and Chen, W. (2011). Simple pyrolysis of urea into graphitic carbon nitride with recyclable adsorption and photocatalytic activity. *Journal of Materials Chemistry*, 21(38): 14398-14401.
- Kang, J. H., Kim, T., Choi, J., Park, J., Kim, Y. S., Chang, M. S. and Park, C. R. (2016). Hidden second oxidation step of Hummers method. *Chemistry of Materials*, 28(3): 756-764.
- Son, W.-J., Kim, J., Kim, J. and Ahn, W.-S. (2008). Sonochemical synthesis of MOF-5. *Chemical Communications*, 44(47): 6336-6338.
- Kang, J. S., Won, J., Park, H. C., Kim, U. Y., Kang, Y. S. and Lee, Y. M. (2000). Morphology control of asymmetric membranes by UV irradiation on polyimide dope solution. *Journal of Membrane Science*, 169(2): 229-235.
- Dutrow, B. and Clark, C. (2015). X-ray powder diffraction (XRD), geochemical instrumentation and analysis. Access from http://serc.carleton.edu/research_education/geochemsheets/techniques/XRD.html [Accessed online: 20 March 2020].
- Hummers, W. S. and Offeman, R. E. (1958). Preparation of oxide. *Journal of the American Chemical Society*, 80(6): 1339-1339.
- Guo, L. P., Wang, J., Fu, F. and Wu, Z. (2015). Three dimensional Fe₃O₄-graphene macroscopic composites for arsenate removal. *Journal of Hazardous Materials*, 298: 28-35.
- Olumurewa, K. O., Olofinjana, B., Fasakin, O., Eleruja, M. A. and Ajayi E. O. B. (2017). Characterization of high yield graphene oxide synthesized by simplified Hummers method. *Graphene*, 6(4): 85-98.
- Alam, S. N., Sharma, N. and Kumar, L. (2017). Synthesis of graphene oxide (GO) by modified Hummers method and its thermal reduction to obtain reduced graphene oxide (rGO). *Graphene*, 6(1): 1-18.
- Sheha, E. (2014). Studies on TiO₂/reduced graphene oxide composites as cathode materials for magnesium-ion battery. *Graphene*, 3(3): 36-43.
- Bhargava, R., Wang, S. Q. and Koenig, J. L. (2003). FTIR micro spectroscopy of polymeric systems. *Advances in Polymer Science*, 163: 137-191.
- Raphael, L. (2011). Application of FTIR spectroscopy to agricultural soils analysis. *Fourier Transforms - New Analytical Approaches FTIR Strategies*: pp. 385-404.
- Gao, W. (2015). The chemistry of graphene oxide in Graphene oxide: Reduction recipes, spectroscopy and applications: pp. 61-95.

20. Yang, K., Peng, H., Wen, Y. and Li, N. (2010). Re-examination of characteristic FTIR spectrum of secondary layer in bilayer oleic acid-coated Fe₃O₄ nanoparticles. *Applied Surface Science*, 256(10): 3093-3097.
21. Vlachos, N., Skopelitis, Y., Psaroudaki, M., Konstantinidou, V., Chatzilazarou, A. and Tegou, E. (2006). Applications of Fourier transform-infrared spectroscopy to edible oils. *Analytica Chimica Acta*, 573: 459-465.
22. Gulmine, J.V., Janissek, P. R. Heise, H. M. and Akcelrud, L. (2002). Polyethylene characterization by FTIR. *Polymer Testing*, 21(5): 557-563.
23. Darkwah, K. W. and Ao, Y. (2018). Mini review on structure and properties (photocatalysis) and preparation techniques of graphitic carbon nitride nano-based particles and its application. *Nanoscale Research Letter*, 13(388): 3-15.
24. Huh, Y. S. and Chang, Y. K. (2015). Selective silver ion adsorption onto mesoporous graphitic carbon nitride. *Carbon*, 95: 58-64.
25. Nandi, B. K., Das B., Uppaluri R., Purkait M. K. (2010). Studies on submicron range microfiltration inorganic membranes: Preparation characterization. *Membrane Water Treatment*, 1(2): 121-137.
26. Ranfang, Z., Gaoxiang, D., Weiwei, Z., Lianhua, L., Yanming, L., Lefu, M. and Zhoahui, L. (2014). Photocatalytic degradation of methylene blue using TiO₂ impregnated diatomite. *Advances in Materials Science and Engineering*, 2014: 1-7.
27. Nguyen, H. T. V., Ngo, T. H. A., Do, K. D., Nguyen, M. N., To Dang, N. T., Nong Yuen, T. T. and Anh Vu, V. T (2019). Preparation and characterization of hydrophilic polysulfide membrane using graphene oxide. *Hindawi Journal of Chemistry*, 2019: 1-10.